

## Analytical and Experimental Determination of FML Stiffness and Strength Properties

Monika KAMOCKA

Radosław J. MANIA

*Department of Strength of Materials*

*Lodz University of Technology*

*Stefanowskiego 1/15, 90–924 Łódź, Poland*

*Radoslaw.Mania@p.lodz.pl*

Received (11 December 2015)

Revised (15 December 2015)

Accepted (21 December 2015)

The paper presents application of analytical methods of determining the mechanical properties of Fibre Metal Laminates. Chosen micromechanical methods were employed to predict elastic moduli and strength of FML panels. Prediction was conducted on two levels i.e. micromechanics where properties of a single composite lamina (prepreg) were analyzed, and macro-mechanics to determine properties of a full FML hybrid material. The properties of a single GFR lamina were predicted by Rule of Mixture Method (ROM), inverse Rule of Mixture Method with correction factor, Halpin Tsai Method, Tsai Method and Wilczynski Method application. Properties of full 3–2 FML lay-up were determined using the Rule of Mixtures. Analytical results were verified by experimental tests. Tensile and bending test were performed on rectangular standard coupons of 3–2 FMLs.

*Keywords:* FML, hybrid laminate, mechanical properties, mechanical testing.

### 1. Introduction

Fibre Metal Laminates (FML) are a type of hybrid structural material consisting of alternating metal layers and layers of a fibre reinforced composite. At the beginning as a composite layer aramid epoxy prepreg (ARRAL) was used. However, the anisotropy of aramid made it unable to use ARALL as a component of plates. Nowadays, the most common solution is application of glass epoxy prepreps as a composite component of FML (GLARE) [18,28]. It allows to obtain higher material properties with lower manufacturing costs. The prevalent material for metal sheets is aluminium. The further FML development has brought CARALL - carbon fiber laminate with aluminium lay-ups and next class - titanium instead of aluminium.

This hybrid material system combines the advantages of metallic materials and fibre reinforced matrix. FML are a combination of high stiffness and strength of

the composite layers and good impact strength aluminum alloy resulting in desired properties for aircraft structures [8]. One of the most important advantage of FML laminate is its resistance against crack propagation in aluminium. Their failure mechanisms are rather complex due to their inhomogeneous structures. Good fatigue strength makes lower thickness or higher stresses in FML possible. Thus thin-walled sections which are commonly used in industry, are prone to buckling [6, 23, 24].

Mechanical properties of particular material - here FML, could be obviously determined by experiment or Finite Element Method [3, 29]. These properties could be also predicted by analytical methods. Considerable research [1, 4, 10, 28] has focused on micromechanical behaviour of lamina and its dependence on applied components. Most studies were based on the Rule of Mixture [2, 11], where the usefulness of those method were investigated. One can find papers [4, 13, 26] which present a great compatibility of the Rule of Mixtures with experiment. Chawla [9] in his work noticed that analytical formulas gave higher results of FML mechanical properties. He pointed out some factors as residual stresses or the mode of deformation of two components which make that ROM is not valid for metal matrix composite. But other researches as Verolme [35], present in his work confirmation of a good agreement between analytical predictions by the Rule of Mixture and experiment. Nevertheless, they suggest more study to verify this concept. He highlights also that the mechanical properties of the FML singular components should be experimentally determined. Similar conclusion one can find in [1, 2, 26] where the analytical predictions were verified by numerical experiment with successful results. Lee at all [22] use the Rule of Mixture to determine in-plane mechanical properties of polypropylene sandwich FML. Authors got a good coherence between experiment, analytical and numerical model. Some discrepancies were observed above the yield limit in the elastic-plastic regime. Ginger at all [13] focused on transverse mechanical properties. He used micromechanical approach referring to reinforcement of factor  $\xi$  applied in Halpin-Tsai Method. In the case of transverse properties some correction factors are required to come closer to the real values [15, 20, 21].

This brief literature survey proves that micromechanical model allows to determine mechanical properties of hybrid composite materials. In this study the usefulness of Rule of Mixture to predict mechanical properties of composite and FML structure is verified and highlighted.

## 2. Materials and method

The FML examined in this work was made of three layers of 2024 T3 aluminium alloy of 0.3 mm nominal thickness whereas two doubled prepreg layers were made of Hexcel R-glass with nominal cured thickness of 0.25–0.26 mm and 60% nominal fibre volume fraction. Four different stacking sequences given in Tab. 1 were considered.

In Tab. 1 "Al" indicates aluminium sheets which "0" orientation coincides with rolling direction. The orientations  $0^\circ$ ,  $25^\circ$ ,  $90^\circ$  of the fibreglass laminae are also measured with respect to the rolling direction of metal layers. The GFR layer lay-ups correspond to commercial GLARE type versions as well as were chosen due to some specific composite futures. The hybrid composite was fabricated at

Table 1 Arrangement of FML laminate

Arrangement code	Lay - up
1	Al/0/90/Al/90/0/Al
2	Al/90/0/Al/0/90/Al
5	Al/0/0/Al/0/0/Al
7	Al/0/25/Al/25/0/Al

Lublin University of Technology. FML panels were cured in autoclave process under vacuum [6, 7]. Nominal thickness of the entire cured laminate was 1.9 mm. However, the measurement of the thickness of the manufactured samples gave higher values of the total thickness. The actual thickness of FML samples was varying from 1.92 to 2.04 mm. These values were adopted in analytical calculations. The declared mechanical properties of both FML constituents given by LUT are outlined in Tab. 2. Properties with subscript ‘3’, usually required in FEM models were obtained due to assumed transversally isotropy of lamina cross section [3].

Table 2 Mechanical properties of FML constituents

Al 2024-T3	[ GPa ]	R-glass prepreg	[ GPa ]
E	72	$E_{L(1)}$	46.43
$\nu$	0.33	$E_{T(2)}$	14.92
G	$E/2(1+\nu)$	$E_{(3)}$	14.92
		$G_{12}$	5.233
		$G_{23}$	3.570
$R_{0.2}$	$359 \times 10^{-3}$	$G_{13}$	5.233
$E_{tang}$	$E \times 10^{-3}$	$\nu_{12} = \nu_{13}$	0.269
		$\nu_{23}$	0.400

3. Analytical prediction of lamina mechanical properties

It may not always be practical to determine each material properties experimentally, therefore some methods have been developed to avoid this problem. Applicability of certain methods to FML structures was confirmed in several works [5, 19, 27, 35] and was verified in current paper as well. Due to conjunction of metal and composite layers the FML obtained its specific features and properties. Thus it should be not treated as metal nor composite but as true hybrid material. Particularly it is visible in a lack of FML direct test standards. However, the mechanical and utility FML attributes are governed directly by both its constituents. Consequently according to the level of study: micro-, meso- or macromechanics material model can be adopted and considered.

When at the micromechanical level to the analysis of unidirectional fiber composite one introduces some basic assumptions and approximations, and neglects the heterogeneous structure of a single lamina - it is smears the matrix and the fibers, and then will achieve the ability to determine mechanical properties of a

lamina in terms of both constituent materials with comparatively simple formulas. Generally it is assumed that both materials are homogenous and elastic in this model. Additionally, when the two-dimensional arrangement of a lamina is accepted, a transversally isotropic composite can be considered. Within the cross-section of a lamina the requirement of statistical homogeneity is fulfilled while in its plane an orthotropy results. Both composite constituents participate in composite straining and stress transfer whereas potential voids (generally void volume fraction is less than 1%) are neglected. This approach lies at the basis of the Rule of Mixtures (ROM) and the inverse Rule of Mixtures (iROM) e.i. Voigt and Reuss models [1, 20]. Both models do not require the knowledge of exact stress and strain fields within the composite and neglect the interaction between constituents due to different Poisson ratio values simply adopting the spring system models. The experimental experience confirms that ROM is insensitive to this assumption yet some underestimation of transverse modulus and in-plane shear modulus is observed [1]. Then some empirical relation or correction factors are introduced [15].

In the subsequent study the mechanical properties of FML structure were predicted in analytical way at two levels – first for a single Glass Fiber Reinforced Epoxy lamina, next the technique was extended to multilayered FML panel. At the micro-level one assumes that a lamina consists of two components: fibres and epoxy matrix with known material properties and volume fraction of each of them. Next, at the macro-level each layer is treated as homogeneous, orthotropic and linearly elastic. To investigate the strength and stiffness characteristics at the first level the Rule of Mixtures [1, 20, 17], Wilczynski method [21, 33], Tsai [20] and the Halpin-Tsai equation [15, 32] were employed. The latter – the rule of Mixtures was applied for multilayered FML coupon. In introduced next formulas the indices  $f$  refer to fibre and  $m$  to matrix, respectively, whereas for elastic moduli classical notation of solid mechanics is introduced.

Employed in the current prediction analysis the Rule of Mixture, Wilczyński and Halpin-Tsai Method use the same formulas to determine the apparent (or effective) modulus in fiber direction and to predict in-plane Poisson's ratio. Specifying fibre volume fraction by  $V_f$  and for matrix as  $V_m$ , these formulas are as follows:

- longitudinal modulus

$$E_1 = V_f E_{1f} + V_m E_m \quad (1)$$

- longitudinal Poisson's ratio

$$\nu_{12} = V_f \nu_{12f} + V_m \nu_m \quad (2)$$

Repeating the rule of mixtures the ultimate strength of composite material can be determined by the following equation:

$$\sigma_{c\max} = V_f \sigma_{f\max} + V_m \sigma_{m_{cf}\max} \quad (3)$$

where:  $\sigma_{f\max}$  – maximum fibre tensile strength,  $\sigma_{m_{cf}\max}$  – matrix stress at a matrix strain equals the maximum tensile strain in the fibres [20].

To determine transverse lamina properties each applied method use different approach. So called in literature "inverse" ROM assumes equality of stresses in fibres and matrix what allows to calculate elastic properties according to following formulas:

- transverse modulus

$$\frac{1}{E_2} = \frac{V_m}{E_m} + \frac{V_f}{E_f} \quad (4)$$

- shear modulus

$$\frac{1}{G_2} = \frac{V_m}{G_m} + \frac{V_f}{G_f} \quad (5)$$

The theoretical assumptions of the "inverse" ROM method lead however to inconsistency with measured results [2]. Numerous experimental tests showed that matrix has significantly higher influence on the transverse properties than it arises from iROM formulas. Tsai introduced  $\nu_{cor}$  correction factor to formulas (4) and (5) to decrease incompliance with experiment, including matrix softness, fibers misalignment and nonuniform stress distribution within the matrix and fibers [32]. Value of a correction factor could vary from 0 to 1 and should be determined by the fit curve technique. From Tsai analysis for  $E_2$  and  $G_{12}$  modulus better estimation than from iROM was provided when  $\nu_{cor} = 0.5$  [32].

$$\frac{1}{E_2} = \frac{\frac{V_f}{E_f} + \frac{\nu_{cor} * V_m}{E_m}}{\nu_{cor} * V_m + V_f} \quad (6)$$

$$\frac{1}{G_{12}} = \frac{\frac{V_f}{G_f} + \frac{\nu_{cor} * V_m}{G_m}}{\nu_{cor} * V_m + V_f} \quad (7)$$

For the range of considered in current analysis material properties this correction factor was assumed as equal to  $\nu_{cor} = 0.4$ .

In his approach Wilczynski (further designated as WM method) assumed the periodic microstructure effect of fibers distribution and focused on a single cell (RVE) with unit dimensions and known volume fraction  $V_f$ , to set formulas for apparent moduli [21, 33]. His formulas are as follows:

- transverse modulus

$$E_2 = E_m \frac{E_m(1 - \sqrt{V_f}) + E_f \sqrt{V_f}}{E_m(1 - \sqrt{V_f}(1 - \sqrt{V_f})) + E_f(1 - \sqrt{V_f}(1 - \sqrt{V_f}))} \quad (8)$$

- shear modulus

$$G_2 = G_m \frac{G_m(1 - \sqrt{V_f}) + G_f \sqrt{V_f}}{G_m(1 - \sqrt{V_f}(1 - \sqrt{V_f})) + G_f(1 - \sqrt{V_f}(1 - \sqrt{V_f}))} \quad (9)$$

Halpin and Tsai took into consideration fibres and packing geometry by introducing parameter  $\xi$  as a measure of fiber reinforcement efficiency for transverse loading of a composite. For circular fibers (as glass fibers are) distributed in a square array  $\xi = 2$  for calculation of  $E_2$  and  $\xi = 1$  for  $G_{12}$  computation. In [13] the choice of parameter  $\xi$  is discussed and "a better estimation" for the usual volume fractions found in practice for a unidirectional lamina of fiber reinforced composites is suggested. Thus effective transversal and shear elastic moduli of the composite according to Halpin–Tsai formulation are given by:

- transverse modulus

$$E_2 = \frac{E_m(1 + \xi\chi V_f)}{1 - \chi V_f} \quad (10)$$

where the coefficient

$$\chi = \left( \frac{E_f}{E_m} - 1 \right) / \left( \frac{E_f}{E_m} + \xi \right)$$

- shear modulus

$$G_{12} = \frac{G_m(1 + \xi\chi V_f)}{1 - \chi V_f} \quad (11)$$

where similarly

$$\chi = \left( \frac{G_f}{G_m} - 1 \right) / \left( \frac{G_f}{G_m} + \xi \right)$$

The last chosen analytical method – Tsai method takes into account some inaccuracies of manufacturing process. He noticed that for composite - mainly with high value of volume fraction, fibres couldn't be fully isolated. Therefore the misalignment factor  $k$  and continuity factor  $C$  were introduced. Both factors are highly dependent on manufacturing process. The parameter  $k$  changes from 0.9 to 1 when  $C$  could vary from 0 to 1. The lower values correspond to isolated fibers and upper to a perfect contiguity. In our analysis it was assumed that  $C = 0.3$  and  $k = 0.93$ . The corresponding expressions take the form:

- longitudinal modulus

$$E_1 = k * (V_f E_{1f} + V_m E_m) \quad (12)$$

- transverse modulus

$$E_2 = 2[\nu_{12f} + (\nu_{12f} - \nu_{12m})V_m] \cdot \left[ (1 - C) \frac{K_f(2K_m + G_m) - G_m(K_f - K_m)V_m}{(2K_m + G_m) + 2(K_f - K_m)V_m} \right] \quad (13)$$

where:

$$K_f = \frac{E_f}{2(1 - \nu_f)} \quad (14)$$

$$K_m = \frac{E_m}{2(1 - \nu_m)} \quad (15)$$

- longitudinal Poisson's ratio

$$\begin{aligned} \nu_{12} = (1 - C) & \frac{K_f \nu_f (2K_m + G_m) V_f + K_m \nu_m (2K_f + G_m) V_m}{K_f (2K_m + G_m) - G_m (K_f - K_m) V_m} \\ & + C \frac{K_m \nu_m (2K_f + G_f) V_m + K_f \nu_f (2K_m + G_f) V_f}{K_f (2K_m + G_m) + G_m (K_m - K_f) V_m} \end{aligned} \quad (16)$$

- shear modulus

$$G_{12} = (1 - C) G_m \frac{2G_f - (G_f - G_m)V_m}{2G_m + (G_f - G_m)V_m} + C G_f \frac{(G_f + G_m) - (G_f - G_m)V_m}{(G_f + G_m) + (G_f - G_m)V_m} \quad (17)$$

To compare in further discussion the glass lamina elastic modulus values determined with application of aforementioned formulas with nominal properties given by the manufacturer, some material data was required. But, mechanical properties for this kind of glass fibers given in different sources differ significantly. Due to a lack of compliance in fiber properties data, few different datasets were selected to perform calculations. These properties for matrix and fibres are given in Tab. 3 with the reference source. For both constituent an isotropic material model was established. The extreme dataset I and V were taken as bound values in further calculations. The dataset V is based on the R-fiber manufacturer official information [36]. Comparing nominal values of I dataset, the lowest modulus can rather be associated with E-glass fibers. However, a variety of data in literature is misleading.

Applying above presented micromechanical prediction formulas there were some numerical calculations performed. Results of them for appointed extreme dataset are summarized in the two tables with reference to both fibre properties dataset. The relative error placed in columns to the right of computed values– which refers to the data declared by FML manufacturer, is also presented for comparison and assessment.

Table 3 Reference lamina material constituent properties

	Matrix [1, 17]	Fibres				
		I Dataset [34]	II Dataset [14, 16]	III Dataset [8, 34]	IV Dataset [26]	V Dataset [36]
E [MPa]	3 500	72 000	76 000	85 000	83 000	87 500
PR	0.40	0.14	0.22	0.23	0.30	0.20
G [MPa]	1821	31 579	31 000	34 553	31 923	36 458

Table 4 Lamina apparent properties

I Dataset								
	ROM	Relative error [%]	WM	Relative error [%]	H-T	Relative error [%]	Tsai	Relative error [%]
E <sub>1</sub> [MPa]	44600	-3.94	44600	-3.94	44600	-3.94	41478	-10.67
E <sub>2</sub> [MPa]	8155	-45.34	12805	-14.18	14887	-0.22	14694	-1.51
PR <sub>12</sub>	0.244	-9.29	0.244	-9.29	0.244	-9.29	0.225	-16.36
G <sub>12</sub> [MPa]	2994	-42.78	6456	+23.37	4420	-15.54	7460	+42.56

Table 5 Lamina apparent properties

V Dataset								
	ROM	Relative error [%]	WM	Relative error [%]	H-T	Relative error [%]	Tsai	Relative error [%]
E <sub>1</sub> [MPa]	53900	+16.09	53900	+16.09	53900	+16.09	50127	+7.96
E <sub>2</sub> [MPa]	8255	-44.67	13210	-11.46	15500	+3.98	15069	+1.00
PR <sub>12</sub>	0.280	+4.09	0.280	+4.09	0.280	+4.09	0.273	+1.49
G <sub>12</sub> [MPa]	4236	-19.05	6632	+26.73	4498	-14.05	7461	+42.58

Comparing calculated values of lamina effective mechanical properties with data obtained from manufacturer (Tab. 2) one can notice some discrepancies. Despite a relatively good agreement with longitudinal Young moduli values (Fig. 1) and Poisson’s ratio values for dataset L, for all three employed methods, generally these



results cannot be accepted. Coincidence in longitudinal Young’s modulus values results obviously of identical or very similar (Tsai method) formulas applied in all methods. The scattered results of transverse elastic modulus and shear modulus confirmed that these mechanical property prediction requires methods where local stress and strain fields should be considered [1]. As suspected the inverse ROM gave serious underestimation of these moduli values with respect to experimental data – here nominal data. Consideration of some misalignment of manufacturing process in Tsai method gave significantly good results in case of transverse Young Modulus. However, this approach gave the greatest values of shear modulus. Moreover significantly discrepancy is visible in determining shear modulus- the Rule of Mixture and Halpin – Tsai method gave underestimation results when two other methods present greater values than nominal data. The next two figures (Figs 2–3) present comparison of all predictions with relative error referred to the property given by the fiber glass prepreg provider.

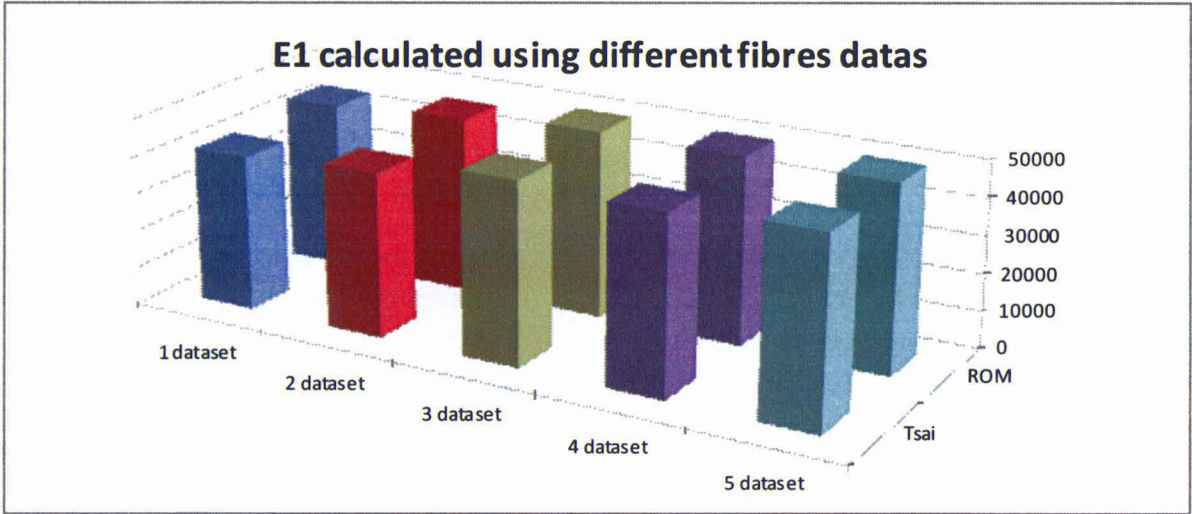


Figure 1 Calculated  $E_1$  lamina modulus

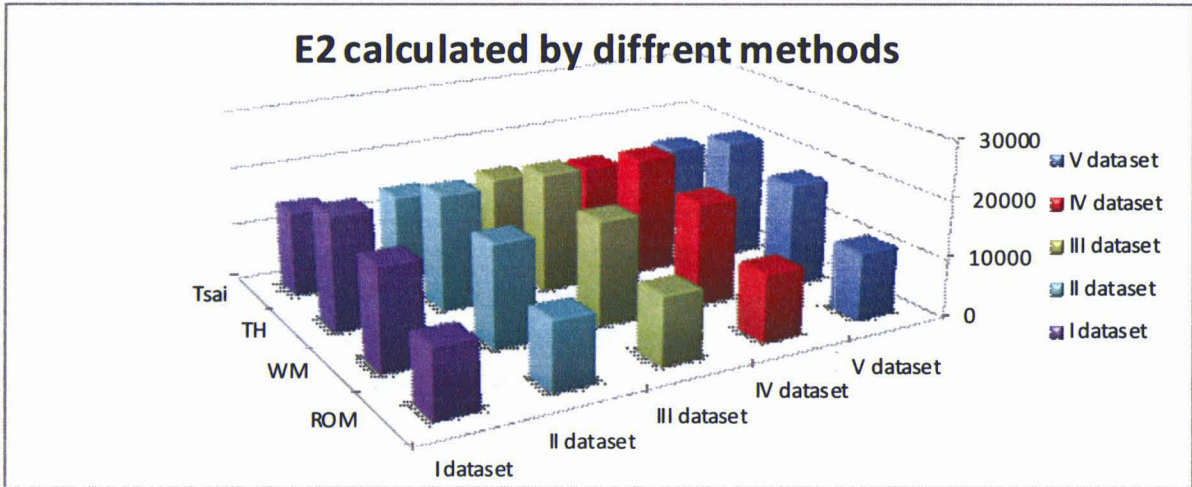


Figure 2 Calculated  $E_2$  lamina modulus

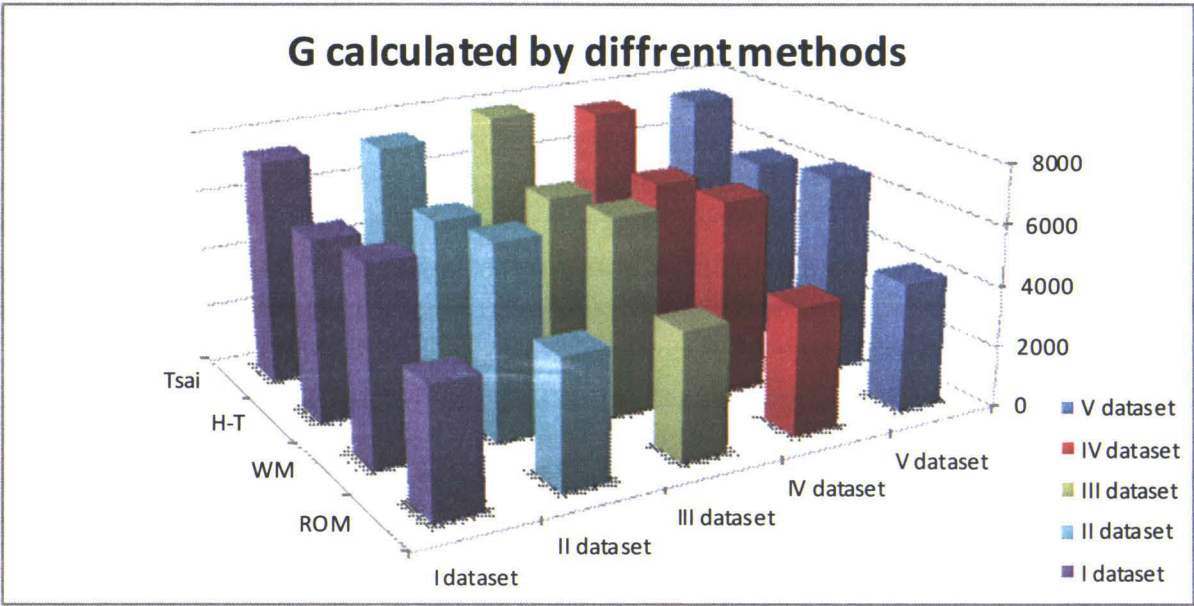


Figure 3 Calculated  $G_{12}$  lamina modulus

Employing Tsai formulas (6) and (7) with correction factor  $\nu_{cor} = 0.4$  the prediction can be improved. The updated modulus values are given jet in Tab. 6. The difference between refined on values and nominal ones decreased significantly and this prediction gave fully satisfactory results placing them within acceptable engineering accuracy range.

Table 6 Transverse and shear modulus with relative error in compersion data from manufacturer

	I Dataset		V Dataset	
$E_2$ [MPa]	14602	-2.13%	14924	+0.02%
$G_{12}$ [MPa]	5412	+3.42%	5488	+4.87%

Concluding this part of the analysis updated results for a single lamina are put together in Fig. 4 for longitudinal elastic modulus  $E_2$  and in Fig. 5 for in-plane shear modulus  $G_{12}$ . These results were determined for dataset I and dataset V and can be taken as a lower and upper bound of obtained lamina mechanical properties. The lowest values gave the inverse ROM method for both transverse and shear moduli, the next two methods predicted in opposite way both moduli nonetheless. The difference between extreme values is then ca 90% for  $E_2$  and 120% for  $G_{12}$ , respectively. To emphasize this inconsistency the determined results for dataset I and V are compared in common plot below. Results for ROM with Tsai correction determined with I dataset are close to the reference elastic properties of prepreg (Tab. 2) whereas the data received based on V dataset convinced of "better" response possibility of applied GFR lamina. These two dataset results will be applied later for a whole FML plate effective elastic properties prediction.



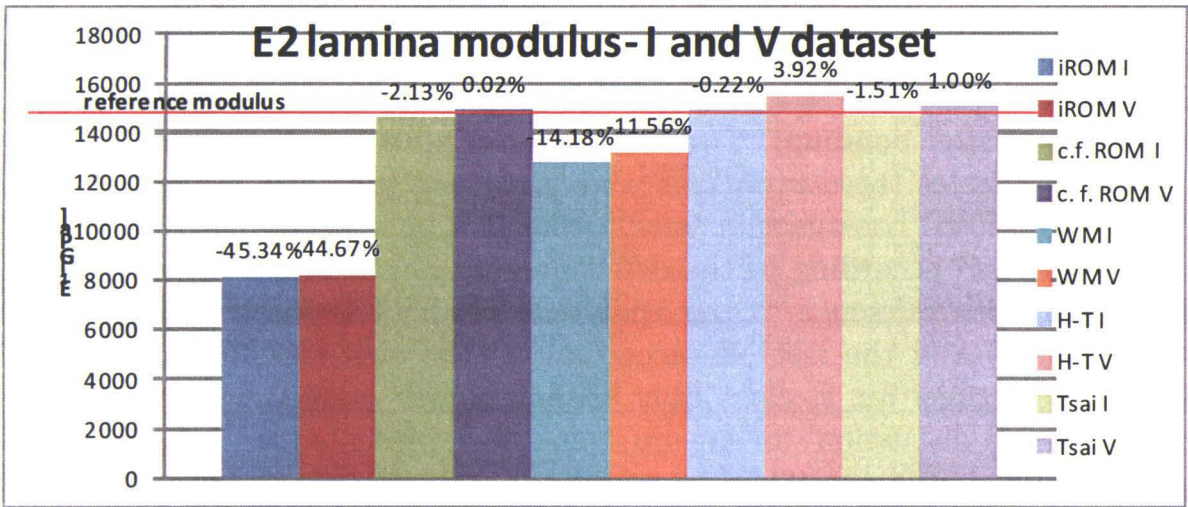


Figure 4  $E_2$  determined by different methods for  $I$  and  $V$  dataset

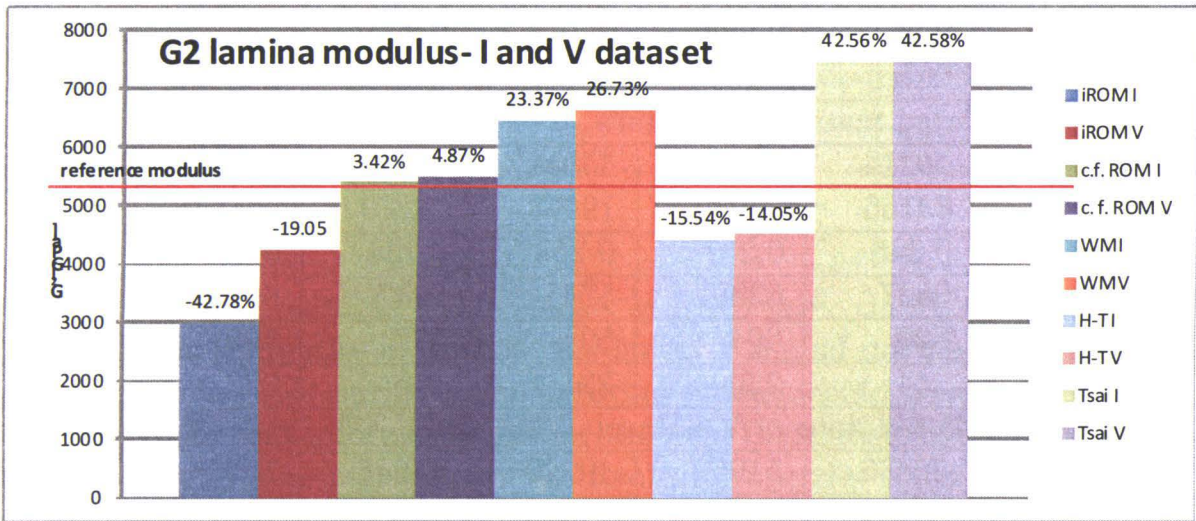


Figure 5  $G$  determined by different methods for  $I$  and for  $V$  dataset

4. FML coupons properties prediction

The micromechanical formulas employed to determination of elastic moduli of composite lamina, could be applied directly to the whole multilayered FML structure. The volume fraction of metal and composite can be determined with relation to the thickness of both constituents within the specimen. Calculations were performed with assumption that the nominal single prepreg layer thickness  $t_{com} = 0.25$  mm and aluminium nominal single layer thickness was  $t_{alu} = 0.3$  mm. However, real dimensions of the specimen investigated during laboratory test differ from nominal one. Thus assumptions were made as taking into account possible aluminium sheet thickness tolerance and the presence of interlayer adhesive at the metal–composite interface introduced during gluing process. Moreover due to greater measured thick-

ness of each tested coupon than the sum of all layers nominal thicknesses (according to manufacturer data) thus for further calculations it was assumed that FML coupon consists of three components – prepreg, aluminium layer and matrix layer (as remaining after bonding). Then due to some potential dimensional possibilities of layer thicknesses these variations were examined too. Few different mechanical properties of FML constituents were assumed – once according to nominal data (Tab. 2), second according to the determined in our tensile test aluminium properties, next with reference to the analytical predictions for R-glass fiber lamina (upper bound) and the last one according to the own aluminium data concerning the predictions for E-glass fiber lamina (lower bound). Detailed results of this ‘numerical discussion’ for lay-up 1 and 2 are presented in Tab. 7. The stacking sequence [Al/0/90/Al/90/0/Al] and [Al/90/0/Al/0/90/Al] have no influence on tensile properties so the calculations are performed together. Other sequences have been calculated in analogous way and are presented in Tab. 8.

**Table 7** FML properties for different options [Al/0/90/Al/90/0/Al] and [Al/90/0/Al/0/90/Al]

	al. 0.3 prepreg 0.25	al. 0.3 prepreg 0.25 + matrix	al. 0.32 prepreg 0.25 + matrix	al. 0.28 prepreg 0.25 + matrix	Mean	STD
based on declared manufacturer data						
E <sub>1</sub> [MPa]	49214	47582	45858	44420	46768	2081
E <sub>2</sub> [MPa]	34166	22479	19673	24373	25173	6299
PR <sub>1–2</sub>	0.245	0.257	0.258	0.239	0.250	0.009
G [MPa]	8647	6399	5745	6847	6910	1244
R <sub>m</sub> [MPa]	620	604	595	577	599	18
R <sub>02</sub> [MPa]	244	230	221	215	228	13
based on predicted data of V dataset						
E <sub>1</sub> [MPa]	52836	51069	49220	47685	50203	2236
E <sub>2</sub> [MPa]	33184	22065	19343	23883	24619	6007
PR <sub>1–2</sub>	0.229	0.242	0.244	0.225	0.235	0.009
G [MPa]	9374	6773	6044	7262	7363	1431
R <sub>02</sub> [MPa]	203	218	196	191	202	12
based on predicted data of I dataset						
E <sub>1</sub> [MPa]	50388	48712	46845	45379	47831	2183
E <sub>2</sub> [MPa]	31560	21362	18796	23078	23699	5528
PR <sub>1–2</sub>	0.219	0.233	0.234	0.216	0.225	0.009
G [MPa]	7850	5967	5390	6361	6392	1051
R <sub>02</sub> [MPa]	203	218	187	181	197	16

From the obtained results it is clearly visible that using declared data from manufacturer FML mechanical properties have been decreased. Similar effect can be observed when taking into account thin adhesive plies. On the other hand assuming higher allowable tolerances especially for aluminium layers elastic moduli values increase. The standard deviation presented in the right side column is relatively high

Table 8 FML properties for different variations [Al/0/0/Al/0/0/Al]

	[Al/0/0/Al/0/0/Al]					
	declared manufacturer data		calculated based on V dataset		calculated based on VI dataset	
	Mean	STD	Mean	STD	Mean	STD
E <sub>1</sub> [MPa]	54635	2257	60080	2457	55518	STD
E <sub>2</sub> [MPa]	28302	3632	29006	5667	27523	4939
PR <sub>1-2</sub>	0.295	0.009	0.287	0.009	0.267	0.009
G [MPa]	6910	1244	7363	1431	6392	1051
R <sub>m</sub> [MPa]	724	185				
R <sub>02</sub> [MPa]	272	12	242	12	228	17
	[Al/25/0/Al/0/25/Al]					
	declared manufacturer data		calculated based on V dataset		calculated based on I dataset	
	Mean	STD	Mean	STD	Mean	STD
E <sub>1</sub> [MPa]	48448	2118	53182	2302	49775	2226
E <sub>2</sub> [MPa]	24693	2182	25755	3555	23912	2974
PR <sub>1-2</sub>	0.314	0.010	0.318	0.010	0.317	0.010
G [MPa]	7229	1372	8013	1721	7120	1330
R <sub>m</sub> [MPa]	628	39				
R <sub>02</sub> [MPa]	229	29	214	12	205	17

[12]. So considered possible discrepancies of FML layer thicknesses influence the apparent elastic properties in limited way however should not be neglected. Different inaccuracy possible during manufacturing process could have similar influence [5, 25]. Without exact information concerning real thicknesses of component we got some boundaries where real value of mechanical properties could exist.

5. Experimental results

Analytical prediction was verified by experimental test where mechanical properties including yield limit and Young’s modulus were investigated. All considered layer sequences were examined during tensile and bending test. Unfortunately only two specimens of each stacking sequence were available to each test. The overall dimensions of all investigated FML samples are given in Tab. 9.


5.1. FML coupons tensile test

Tensile tests were conducted according to D3039/D3039M-00 in a room temperature conditions [30]. Specimens were mounted in the grips of an universal strength testing machine Instron 4485, upgraded with Zwick/Roell control software (Fig. 6). The elongation was measured an attached strength machine mechanical extensometer. Axial and transverse strains were also measured with the application of two pairs of crossed strain gauges bonded back-to-back on each specimen. The single specimen was loaded until fracture with the loading control of 5 N/mm<sup>2</sup> min<sup>-1</sup>.




**Table 9** Dimensions of FML samples

[mm]	Tensile 1A	Tensile 1B	Tensile 2A	Tensile 2B	Tensile 5A	Tensile 5B	Tensile 7A	Tensile 7B
width	25.00	25.00	24.90	24.97	19.99	19.98	25.00	25.00
total length	150	150	250	250	200	200	150	150
actual thick- ness	2.10	2.00	1.97	1.99	1.97	1.98	1.94	1.95

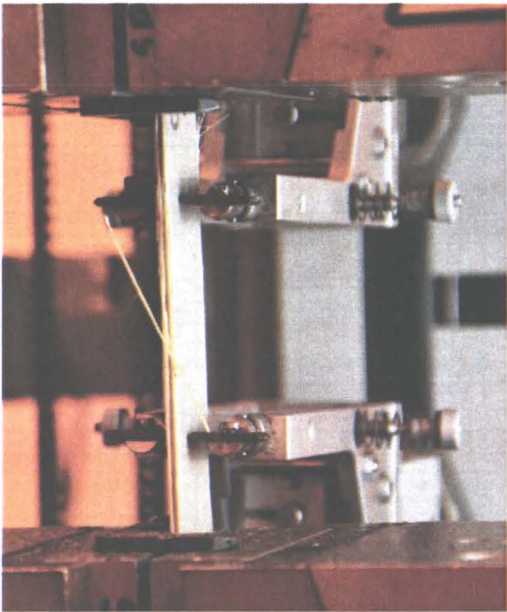

**Figure 6** Specimen placed in the universal testing machine

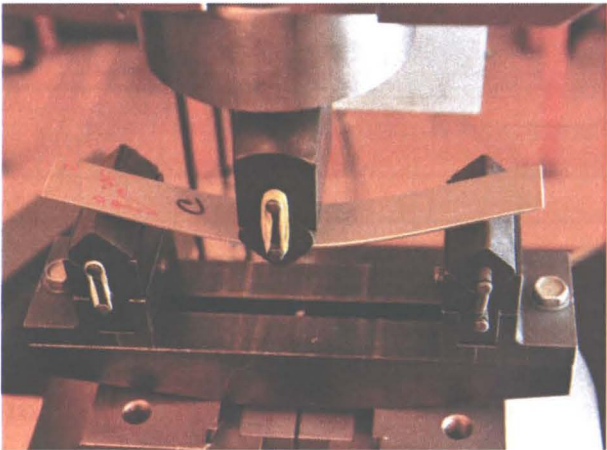

**Figure 7** FML specimen during three point bending test

Results of performed static tensile tests are presented in Tab. 10. It is visible that result of specimen 2B differs significantly from values of other samples what was caused by some inaccuracy in specimen placing in the machine grips. Due to this the value of Young's modulus has been varied and couldn't be taken into consideration during further analyses.

**Table 10** Results of FML specimen tensile test

Test	$a_0$	$b_0$	$S_0$	$E_{axial}$	$R_{p0.2}$	$R_m$	$F_{max}$	$A_t$
Sample	mm	mm	mm <sup>2</sup>	GPa	MPa	MPa	kN	%
1A	2.10	25.00	52.5	50.38	237	700	36.73	8.71
1B	2.00	25.00	50.00	53.75	249	736	36.82	7.25
2A	1.97	24.9	49.05	50.57	247	711	34.87	5.08
2B	1.99	24.95	49.65	37.46	237	691	34.30	5.65
5A	1.99	19.97	39.74	65.89	299	1185	47.08	5.14
5B	2.06	19.98	41.16	60.23	298	1156	47.60	5.44
7A	1.94	25.00	48.5	58.16	276	806	39.10	5.09
7B	1.95	25.00	48.8	59.07	263	812	39.60	4.94

## 5.2. FML coupons flexural test

The flexure test was carried out according to the standard D790-00; procedure B [31], again using the strength machine Instron 4485. The three point bending flexural test allowed to determine the flexural stress-strain response of the FML material. Specimens were mounted over the special flexural fixture of the universal testing machine and gradually (5 mm/min) loaded in bending (Fig. 7). Two different spans of supports were set during the bending (120 and 150 mm). In the flexural test both pairs of 1 and 2 stacking sequences had to be analyzed separately what was not the case for tension.

**Table 11** Results of flexural tests

TEST of	$t_{tot}$	$b_0$	$F_{max}$	$R_g$	$E_{flex}$	$E_{a-flex}(13)$
	mm	mm	N	MPa	GPa	GPa
1A(0/90)	1.92	25.00	197.1	481.2	59.88	59.53
1B	1.92	25.00	192.6	470.3	61.39	60.16
2A(90/0)	1.98	24.95	225.72	415.37	54.93	54.25
2B	2.01	24.99	229.51	409.18	52.51	52.02
5A	1.94	19.97	250.79	600.61	64.57	64.12
5B	1.97	20.03	252.52	584.72	62.62	62.15
7A	1.96	25.00	214.10	501.5	62.81	62.49
7B	2.04	25.00	218.10	471.6	55.89	55.29

According to a three-point bending solution for a composite beam flexural moduli could be determined by the formula:

$$E_{a\_flex} = \frac{F_c}{w_c} \frac{L^3}{4t_{tot}^3b_0} \tag{18}$$

where  $L$  – span of specimen supports (thus  $L/t_{tot} \approx 60 \vee 75$  and the shear effect was reduced in essential way),  $w_c$  – measured deflection for  $F_c$  applied actual bending force and  $t_{tot}$  is a total thickness of actual specimen.

A good agreement between analytical and experimental results presented in Table 11 can be observed. It is also visible that flexural moduli are higher than those indicated during tensile tests what is a common feature.

In Tab. 12 theoretical calculations are compared with results of tensile tests. There the column headings indicate: ROM I results obtained based on manufacturer declared data of FML components (see Tab. 2), II and III results of predictions based on micromechanical approach where components properties were referred to V and I dataset, respectively (see Tab. 3).

Table 12 Results of tensile test

[Al/90/0/Al/0/90/Al] and [Al/0/90/Al/90/0/Al]							
	EXPERIMENT				ROM		
[MPa]	1A	1B	2A	2B	I	II	III
E <sub>1</sub>	50380	53750	50570	37460	46768	50203	47831
R <sub>02</sub>	237	250	247	237	228	202	197
[Al/0/0/Al/0/0/Al]							
	EXPERIMENT				ROM		
	5A		5B		I	II	III
E <sub>1</sub>	65890		60230		54635	60080	55518
R <sub>02</sub>	299		299		272	242	228
[Al/25/0/Al/0/25/Al]							
	7A		7B		I	II	III
E <sub>1</sub>	58160		59070		48448	53182	49775
R <sub>02</sub>	277		263		229	214	205

The higher moduli values correspond better to R-glass prepreg properties than declared by FML manufacturer data what also S confirmed results of buckling experiments conducted on FML short columns of open cross-section profiles [25].

6. Conclusions

In the presented paper the micro- and macromechanics methods were applied at two levels. On micro- level longitudinal and transverse mechanical properties of GFRE were determined basing on Voigt/Reuss tenants, Wilczynski, Tsai method and Halpin-Tsai equations. Significant differences were observed between results determined with applied methods of predicted transverse properties. The highest discrepancies were observed for Tsai method and Halpin-Tsai, where the last method is sensitive to  $\xi$  parameter estimation. Introduced correction factors to Rule



of Mixture formulas gave finally satisfied results. For Fiber Metal Laminate hybrid material the longitudinal properties were indicated by Rule of Mixture. All analytical predictions were verified by experimental tests. It should be emphasized that the thickness of FML components as well as mechanical properties of prepreg and aluminium alloy are crucial factors to predict mechanical properties of FML hybrid material. Even small tolerance deviation gave visible discrepancies in results. Due to that it is impossible to determine exactly mechanical properties without exact component data. The effect of technology - autoclaving assembling, introduction of adhesive layers, decreases the stiffness of entire Fiber Metal Laminate as well as possible changes of fiber orientation. The problem of residual stress influence and rheological interaction of constituents was not considered in performed analysis.

The presented analyses confirmed that mechanical properties of fibreglass reinforced epoxy lamina as well as Fiber Metal Laminate hybrid material could be determined by simply micromechanical formulas.

### Acknowledgment

This study is supported by the Ministry of Science and Higher Education of Poland - National Science Centre Grant No DEC-2012/07/B/ST8/04093.

### References

- [1] **Aboudi, J., Arnold, S. M. and Bednarczyk, B. A.:** Micromechanics of Composite Materials: A Generalized Multiscale Analysis Approach, *Elsevier Science Publishers*, B.V., **2013**.
- [2] **Adams, D. F., Carlsson, L. A. and Pies, R. B.:** Experimental Characterisation of Advanced Composite Materials, *CRC Press*, **2003**.
- [3] **Barbero, E.:** Finite element analysis of composite materials using ANSYS, *CRC Press*, **2014**.
- [4] **Banerjee, S. and Sankar, S. V.:** Mechanical properties of Hybrid Composites using Finite Element Method Based Micromechanics, *Composite, Part B*, 58, pp. 318–327, **2014**.
- [5] **Bienias, A., Majerski, K., Surowska, B. and Jakubczak, P.:** The mechanical properties and failure analysis of selected fiber metal laminates, *Lublin Univ. of Technology*, **2013**.
- [6] **Bienias J., Gliszczyński, A., Jakubczak, P., Kubiak, T. and Majerski, K.:** Influence of autoclaving process parameters on the buckling and postbuckling behaviour of thin-walled channel section beams, *Thin-Walled Structures*, 85, pp. 262–270, **2014**.
- [7] **Bienias, J., Mania, R. J., Jakubczak, P. and Majerski, K.:** The issues of manufacturing geometrically complicated elements using fml laminates, *composites theory and practice*, 15, 4, pp. 243–249, **2015**.
- [8] **Botelho, E. C., Silva, R. A., Pardini, L. C. and Rezende, M. C.:** A review on the development and properties of continuous fiber/epoxy/aluminum hybrid composites for aircraft structures, *Mat. Research*, Vol. 9, No 3, **2006**.
- [9] **Chawla, K. K.:** On the applicability of the "Rule-of-Mixtures" to the strength properties of Metal-Matrix Composites, *Revista Brasileira de Física*, Vol. 4, No. 3, pp. 411–418, **1974**.
- [10] **Composite Materials Handbook Volume 1, MIL-HDBK-17-1F**, **2002**.
- [11] **Daniel, I. M. and Ishai, O.:** Engineering mechanics of composite materials, *Oxford University Press*, **1994**.

- [12] Devore, J. and Farnum, N.: Applied Statistics for Engineers and Scientists, *Duxbury Press*, 1999.
- [13] Giner, E., Franco, V. and Vercher, A.: Estimation of the reinforcement factor  $\xi$  for calculating  $e_2$  with the halpin-tsai equations using the Finite Element Method, *ECCM16 - 16<sup>th</sup> European Conference on Composite Materials*, Seville, Spain, 2014.
- [14] Hagenbeek, M., Van Hengel, C., Bosker, O. J. and Vermeeren, C. A. J. R.: Static Properties of Fibre Metal Laminates, *Delft Univ. of Technology*, 2003.
- [15] Halpin, J. C. and Kardos, J. L.: The Halpin-Tsai equation: a Review, *Polymer Eng. and Scien.*, Vol. 16, No. 5, pp. 344–352, 1976.
- [16] Hartman, D., Greenwood, M. E. and Miler, D. M.: High strength glass fibers, *AGY Technical Report*, No LIT-2006-111 R2, 2006.
- [17] Hashin, Z., Rosen, B. W., Humphreys, E. A., Newton, C. and Chatterjee, S.: Fiber Composite Analysis and Design: Composite Materials and Laminates, Vol. 1, *Report DOT/FAA/AR-95/29*, 1, 1997.
- [18] Iaccarino, P., Langella, A. and Caprino, G.: A simplified model to predict the tensile and shear stress-strain behaviour of fibreglass/aluminium laminates, *Comp. Science and Techno.*, 67, pp. 1784–1793, 2007.
- [19] Jia Xue, Wen-Xue Wang, Jia-Zhen Zhang, Su-Jun Wu, Hang Li: Experimental and numerical study on the tensile behaviour of UACS/Al, *Fibre Metal Laminate*, 2014.
- [20] Jones, R. M.: Mechanics of composite materials, *Taylor & Francis*, 1999.
- [21] Kowal-Michalska K. (ed.): Dynamic stability of composite plate structures, *Scientific and Technical Publishing*, Warsaw, 2007.
- [22] Lee, B. E., Park, E. T., Jeong Kim, J., Kang, B. S. and Song, W. J.: Analytical evaluation on uniaxial tensile deformation behavior of fiber metal laminate based on SRPP and its experimental confirmation, *Composites: Part B*, 67, pp. 154–159, 2014.
- [23] Mania, R. J.: Comparative static buckling study of FML thin-walled profiles, *ECCM16 - 16<sup>th</sup> European Conference on Composite Materials*, Seville, Spain, 2014.
- [24] Mania, R. J.: Buckling and post-buckling of FML compressed open cross section profiles, *3rd Int. Conf. on Buckling and Postbuckling Behaviour of Comp. Lam. Struct.*, Braunschweig, 2015.
- [25] Mania, J. R., Kolakowski, Z., Bienias, J., Jakubczak, P. and Majerski, K.: Comparative study of FML profiles buckling and postbuckling behaviour under axial loading, *Composite Struct.*, Vol. 134, pp. 216–225, 2015.
- [26] Mayer, P. and Kaczmar, J. W.: Properties and application of carbon and glass fibers, *Tworzywa sztuczne i chemia*, 6, pp. 50–55 (in Polish), 2008.
- [27] Moussavi-Torshizi, S. E., Dariushi, S., Sadighi, M. and Safarpour, P.: A study on tensile properties of a novel fiber/metal laminates, *Materials Scien. and Eng. A*, 527, pp. 4920–4925, 2010.
- [28] Sinmazçelik, T., Avcu, E., Bora, M. Ö. and Çoban, O.: A review: Fibre metal laminates. background. bonding types and applied test methods, *Materials and Design*, 32, pp. 3671–3685, 2011.
- [29] Soltani, P., Keikhosravy, M., Oskouei, R. H. and Soutis, C.: Studying the Tensile Behaviour of GLARE Laminates: A Finite Element Modelling Approach, *Appl. Compos. Materials*, 18, pp. 271–282, 2011.
- [30] Standard Test Method for Tensile Properties of Polymer Matrix Composite Materials, *ASTM D 3039/D 3039M-00*, 2002.

- [31] Standard Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials, *ASTM*, D, 790–00, **2001**.
- [32] **Tsai, S. and Hahn, H. T.**: Introduction to Composite Materials, *Technomic Pub. Comp.*, **1980**.
- [33] **Wilczyński, A. P.**: Polymer Fiber Composite, *WNT* (in Polish), **1996**.
- [34] **Wallenberger, F. T., Watson, J. C. and Li, H.**: Glass Fibres. Constituents Materials, *ASM Handbook*, Vol. 21, pp. 27–34, **2001**.
- [35] **Wu, H. F., Wu, L. L., Slagter, W. J. and Verolme, J. L.**: Use of rule of mixtures and metal volume fraction for mechanical property predictions of fibre-reinforced aluminium laminates, *J. of Material Science*, 29, pp. 4583–4591, **1994**.
- [36] Owens Corning webpage, <http://www.ocvreinforcements.com>.